

Internal Transmittance (τ)

λ nm	200	210	220	230	240	250	260	270	280	290	300	310	320	330	340	350	360	370	380	390
τ	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05
λ nm	400	410	420	430	440	450	460	470	480	490	500	510	520	530	540	550	560	570	580	590
τ	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05
λ nm	600	610	620	630	640	650	660	670	680	690	700	710	720	730	740	750	760	770	780	790
τ	<1E-05	<1E-05	<1E-05	<1E-05	0.001	0.044	0.329	0.686	0.886	0.953	0.973	0.980	0.982	0.982	0.984	0.983	0.984	0.983	0.983	0.983
λ nm	800	810	820	830	840	850	860	870	880	890	900	910	920	930	940	950	960	970	980	990
τ	0.983	0.982	0.982	0.982	0.983	0.982	0.982	0.983	0.983	0.984	0.985	0.985	0.986	0.986	0.988	0.988	0.989	0.989	0.989	0.990
λ nm	1000	1010	1020	1030	1040	1050	1060	1070	1080	1090	1100	1120	1140	1160	1180	1200				
τ	0.990	0.991	0.989	0.990	0.991	0.991	0.992	0.992	0.993	0.993	0.993	0.993	0.994	0.994	0.994	0.994				

Refractive Index/Absorption coefficient/Reflection coefficient

λ nm	400	500	600	700	800	900	1000
n	1.546	1.535	1.530	1.526	1.523	1.522	1.521
K	2.6E-03	1.6E-03	4.3E-04	9.8E-07	2.1E-07	5.9E-08	2.0E-08
P	0.912	0.915	0.916	0.917	0.918	0.918	0.918

Classes of Bubbles and Inclusions

Bubble Class
3

Color Specification


	x	y	Y	λ_d	P _e
A	-	-	-	-	-
C	-	-	-	-	-
D65	-	-	-	-	-

Properties

Chemical		Thermal				Mechanical		Others
D _W	D _A	T _g	T _s	$\alpha_{-30/70}$	$\alpha_{100/300}$	H _K	F _A	d
1	1	555	620	94	106	520	140	2.68

Tolerance of Transmittance (τ)

$\lambda\tau$ (nm)	λL (nm)	λH (nm)
665±5	<580	>750

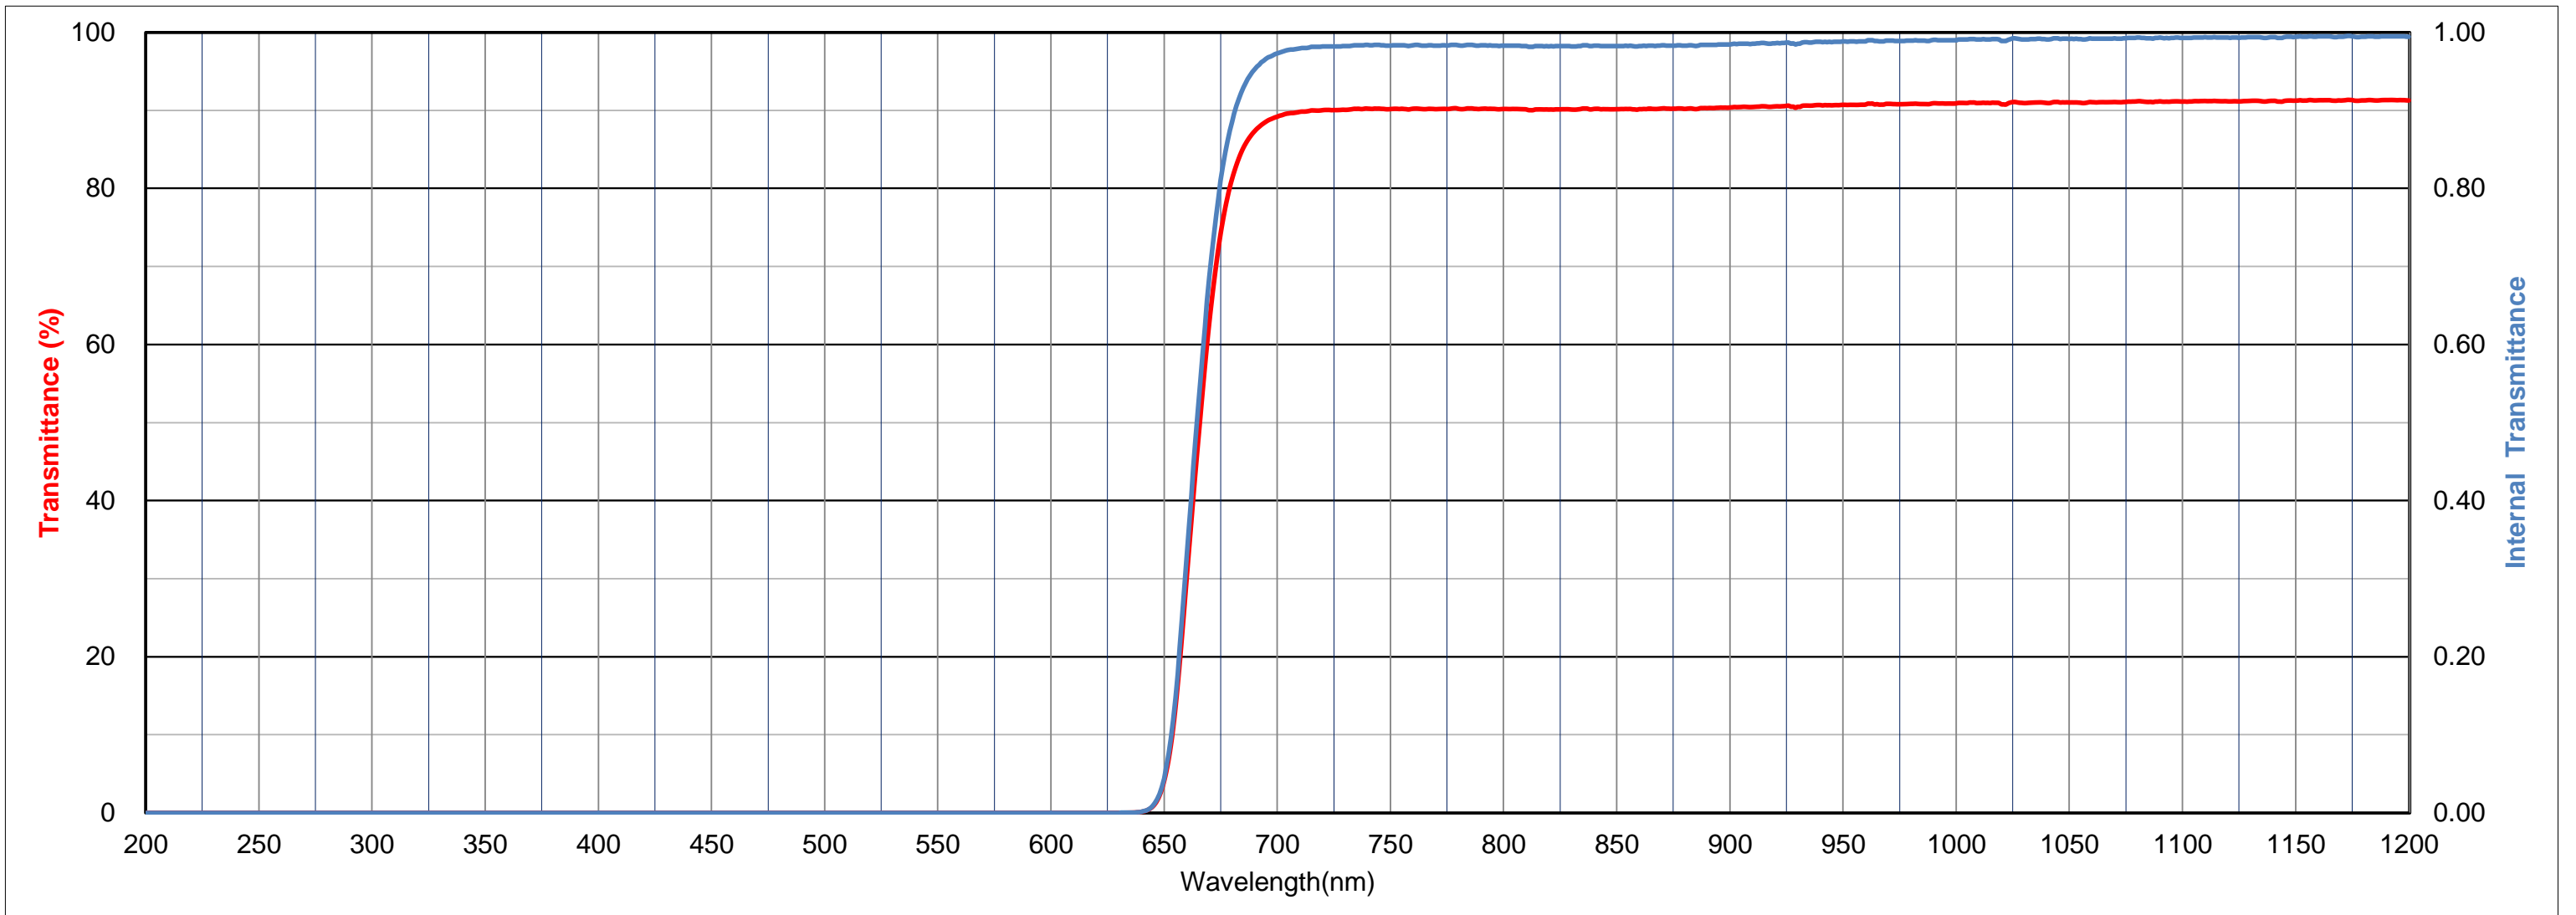

Internal Transmittance (τ)

λ nm	200	210	220	230	240	250	260	270	280	290	300	310	320	330	340	350	360	370	380	390
τ	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05
λ nm	400	410	420	430	440	450	460	470	480	490	500	510	520	530	540	550	560	570	580	590
τ	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05
λ nm	600	610	620	630	640	650	660	670	680	690	700	710	720	730	740	750	760	770	780	790
τ	<1E-05	<1E-05	<1E-05	<1E-05	0.001	0.044	0.329	0.686	0.886	0.953	0.973	0.980	0.982	0.982	0.984	0.983	0.984	0.983	0.983	0.983
λ nm	800	810	820	830	840	850	860	870	880	890	900	910	920	930	940	950	960	970	980	990
τ	0.983	0.982	0.982	0.982	0.983	0.982	0.982	0.983	0.983	0.984	0.985	0.985	0.986	0.986	0.988	0.988	0.989	0.989	0.989	0.990
λ nm	1000	1010	1020	1030	1040	1050	1060	1070	1080	1090	1100	1110	1120	1130	1140	1150	1160	1170	1180	1190
τ	0.990	0.991	0.989	0.990	0.991	0.991	0.992	0.992	0.993	0.993	0.993	0.993	0.993	0.994	0.994	0.994	0.994	0.994	0.994	0.995
λ nm	1200	1210	1220	1230	1240	1250	1260	1270	1280	1290	1300	1310	1320	1330	1340	1350	1360	1370	1380	1390
τ	0.994	0.993	0.994	0.994	0.994	0.994	0.995	0.996	0.996	0.996	0.996	0.997	0.997	0.997	0.997	0.997	0.997	0.997	0.997	0.997
λ nm	1400	1410	1420	1430	1440	1450	1460	1470	1480	1490	1500	1510	1520	1530	1540	1550	1560	1570	1580	1590
τ	0.995	0.994	0.995	0.996	0.997	0.997	0.998	0.997	0.998	0.998	0.998	0.998	0.998	0.999	0.999	0.999	0.999	0.999	0.998	0.998
λ nm	1600	1610	1620	1630	1640	1650	1660	1670	1680	1690	1700	1710	1720	1730	1740	1750	1760	1770	1780	1790
τ	0.999	0.999	0.999	0.999	0.998	0.998	0.998	0.998	0.998	0.998	0.997	0.997	0.997	0.996	0.996	0.995	0.995	0.995	0.994	0.994
λ nm	1800	1810	1820	1830	1840	1850	1860	1870	1880	1890	1900	1910	1920	1930	1940	1950	1960	1970	1980	1990
τ	0.994	0.993	0.993	0.993	0.992	0.992	0.992	0.992	0.992	0.992	0.990	0.991	0.990	0.990	0.990	0.989	0.989	0.988	0.988	0.988
λ nm	2000	2050	2100	2150	2200	2250	2300	2350	2400	2450	2500	2550	2600	2650	2700	2750	2800	2850	2900	2950
τ	0.988	0.986	0.981	0.974	0.964	0.957	0.957	0.956	0.950	0.942	0.934	0.928	0.920	0.909	0.877	0.457	0.274	0.249	0.234	0.219
λ nm	3000	3050	3100	3150	3200	3250	3300	3350	3400	3450	3500	3550	3600	3650	3700	3750	3800	3850	3900	3950
τ	0.205	0.189	0.171	0.154	0.139	0.125	0.113	0.103	0.094	0.087	0.082	0.079	0.081	0.082	0.083	0.090	0.101	0.115	0.120	0.118
λ nm	4000	4050	4100	4150	4200	4250	4300	4350	4400	4450	4500	4550	4600	4650	4700	4750	4800	4850	4900	4950
τ	0.113	0.107	0.101	0.092	0.079	0.064	0.048	0.033	0.020	0.010	0.004	0.001	0.001	0.001	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05
λ nm	5000																			
τ	<1E-05																			

