

λ nm	200	210	220	230	240	250	260	270	280	290	300	310	320	330	340	350	360	370	380	390
τ	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05
λ nm	400	410	420	430	440	450	460	470	480	490	500	510	520	530	540	550	560	570	580	590
τ	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05
λ nm	600	610	620	630	640	650	660	670	680	690	700	710	720	730	740	750	760	770	780	790
τ	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	0.001	0.023	0.301	0.681	0.856	0.914	0.933	0.943	0.946	0.949	0.953
λ nm	800	810	820	830	840	850	860	870	880	890	900	910	920	930	940	950	960	970	980	990
τ	0.954	0.954	0.957	0.958	0.960	0.962	0.963	0.964	0.965	0.967	0.969	0.970	0.971	0.974	0.974	0.975	0.976	0.978	0.979	0.979
λ nm	1000	1010	1020	1030	1040	1050	1060	1070	1080	1090	1100	1120	1140	1160	1180	1200				
τ	0.980	0.981	0.979	0.982	0.982	0.983	0.983	0.984	0.985	0.985	0.986	0.986	0.987	0.989	0.989	0.988				

Refractive Index/Absorption coefficient/Reflection coefficient

λ nm	400	500	600	700	800	900	1000
n	1.567	1.555	1.549	1.545	1.542	1.541	1.540
K	2.2E-04	3.6E-04	4.5E-04	9.2E-05	7.6E-06	8.0E-06	8.1E-06
P	0.907	0.910	0.911	0.912	0.913	0.913	0.914

Classes of Bubbles and Inclusions

Bubble Class
3

Color Specification


	x	y	Y	λ_d	P_e
A	-	-	-	-	-
C	-	-	-	-	-
D65	-	-	-	-	-

Properties

Chemical		Thermal				Mechanical		Others
D_w	D_A	T_g	T_s	$\alpha_{-30/70}$	$\alpha_{100/300}$	H_K	F_A	d
1	3	525	575	100	116	470	160	2.86

Tolerance of Transmittance (τ)

$\lambda\tau$ (nm)	λL (nm)	λH (nm)
715±8	<630	>810

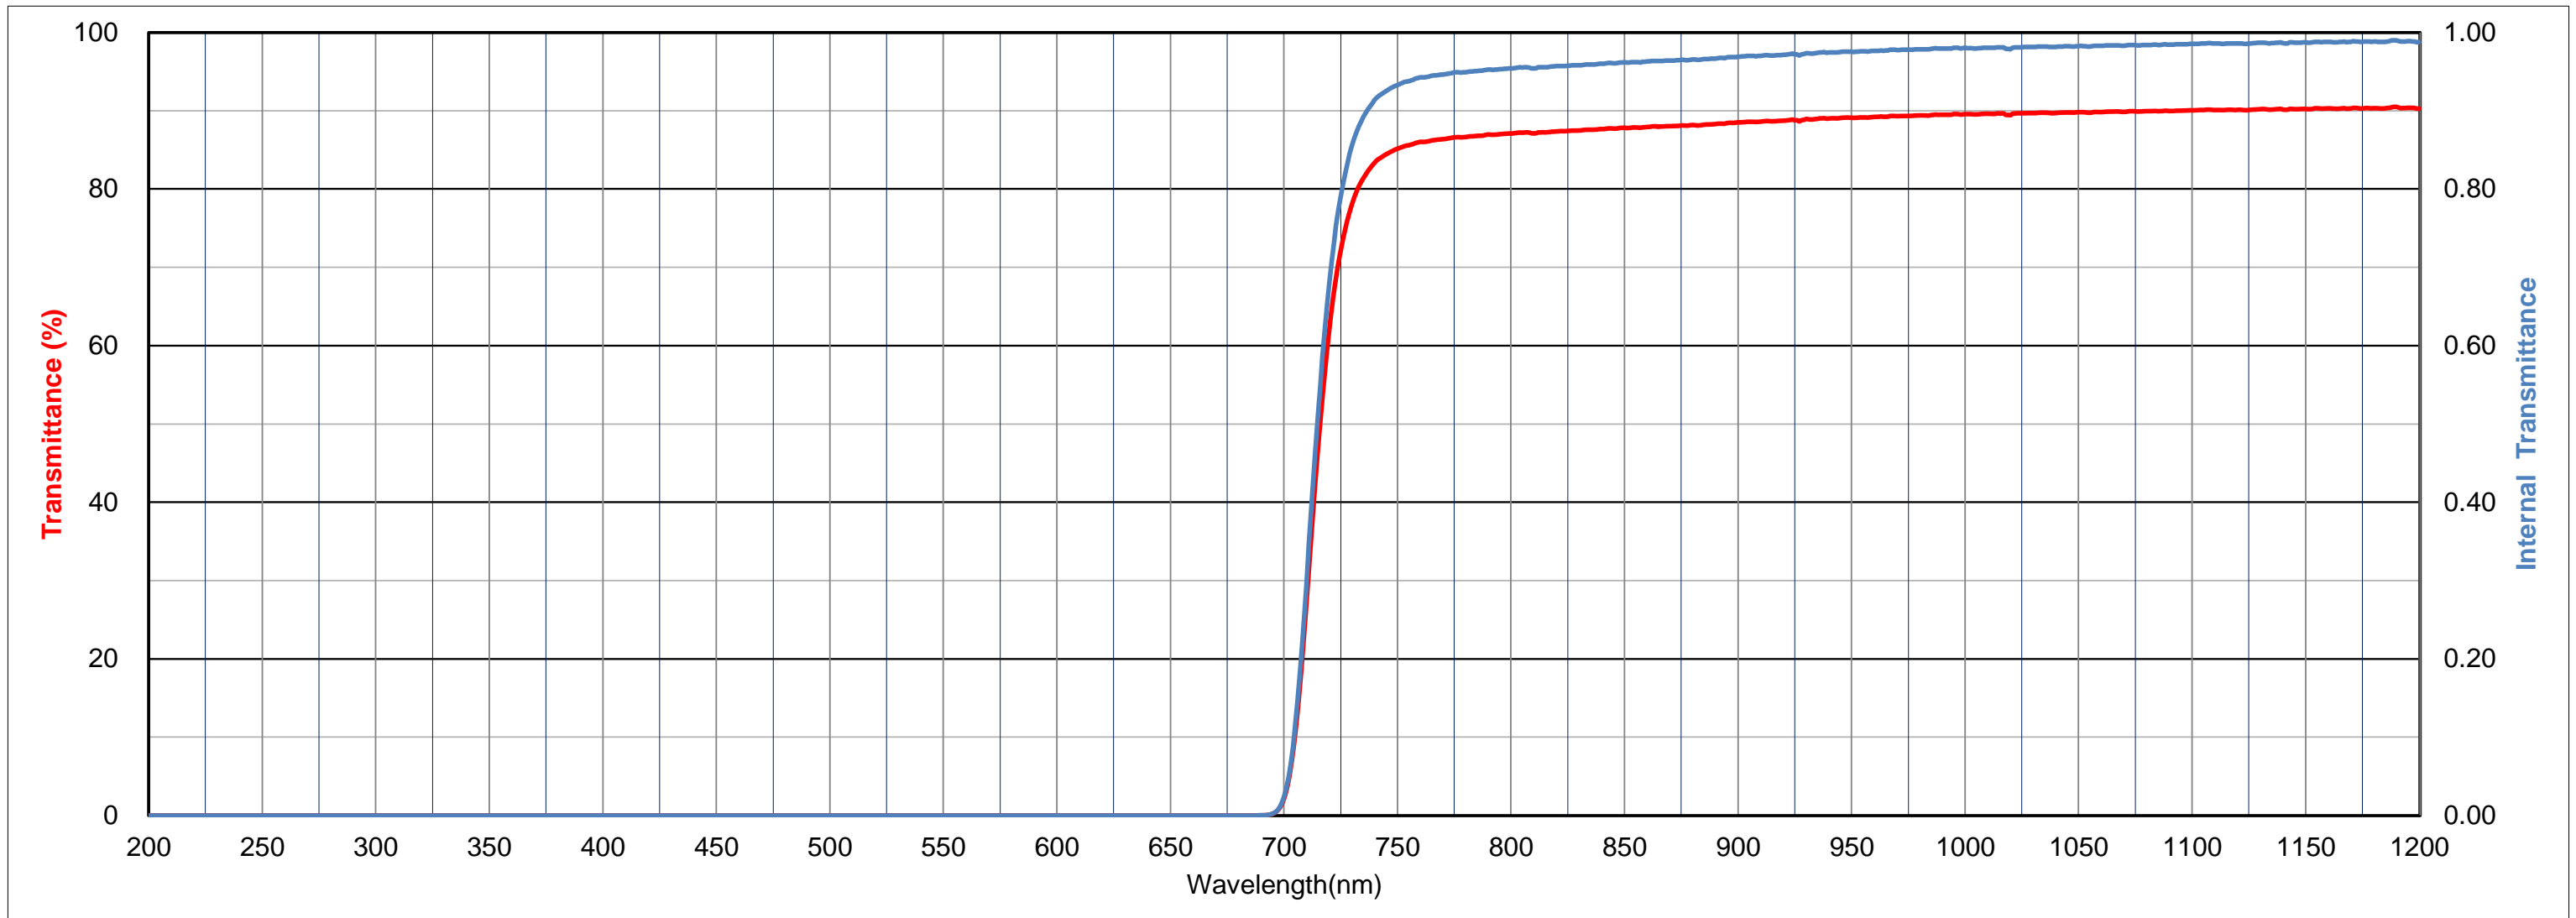

Internal Transmittance (τ)

λ nm	200	210	220	230	240	250	260	270	280	290	300	310	320	330	340	350	360	370	380	390
τ	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05
λ nm	400	410	420	430	440	450	460	470	480	490	500	510	520	530	540	550	560	570	580	590
τ	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05
λ nm	600	610	620	630	640	650	660	670	680	690	700	710	720	730	740	750	760	770	780	790
τ	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	0.001	0.023	0.301	0.681	0.856	0.914	0.933	0.943	0.946	0.949	0.953
λ nm	800	810	820	830	840	850	860	870	880	890	900	910	920	930	940	950	960	970	980	990
τ	0.954	0.954	0.957	0.958	0.960	0.962	0.963	0.964	0.965	0.967	0.969	0.970	0.971	0.974	0.974	0.975	0.976	0.978	0.979	0.979
λ nm	1000	1010	1020	1030	1040	1050	1060	1070	1080	1090	1100	1110	1120	1130	1140	1150	1160	1170	1180	1190
τ	0.980	0.981	0.979	0.982	0.982	0.983	0.983	0.984	0.985	0.985	0.986	0.986	0.986	0.987	0.987	0.988	0.989	0.988	0.989	0.991
λ nm	1200	1210	1220	1230	1240	1250	1260	1270	1280	1290	1300	1310	1320	1330	1340	1350	1360	1370	1380	1390
τ	0.988	0.988	0.989	0.990	0.991	0.990	0.991	0.991	0.992	0.993	0.993	0.993	0.994	0.994	0.994	0.994	0.994	0.995	0.995	0.994
λ nm	1400	1410	1420	1430	1440	1450	1460	1470	1480	1490	1500	1510	1520	1530	1540	1550	1560	1570	1580	1590
τ	0.993	0.992	0.993	0.993	0.994	0.995	0.995	0.995	0.996	0.995	0.995	0.996	0.996	0.996	0.996	0.996	0.996	0.996	0.996	0.996
λ nm	1600	1610	1620	1630	1640	1650	1660	1670	1680	1690	1700	1710	1720	1730	1740	1750	1760	1770	1780	1790
τ	0.996	0.995	0.996	0.995	0.995	0.995	0.995	0.995	0.994	0.994	0.994	0.993	0.993	0.993	0.992	0.992	0.992	0.991	0.991	0.991
λ nm	1800	1810	1820	1830	1840	1850	1860	1870	1880	1890	1900	1910	1920	1930	1940	1950	1960	1970	1980	1990
τ	0.991	0.990	0.990	0.990	0.989	0.990	0.989	0.988	0.989	0.989	0.989	0.989	0.988	0.988	0.988	0.988	0.987	0.987	0.987	0.987
λ nm	2000	2050	2100	2150	2200	2250	2300	2350	2400	2450	2500	2550	2600	2650	2700	2750	2800	2850	2900	2950
τ	0.987	0.986	0.981	0.974	0.966	0.958	0.958	0.956	0.948	0.941	0.937	0.936	0.920	0.908	0.875	0.516	0.244	0.196	0.170	0.149
λ nm	3000	3050	3100	3150	3200	3250	3300	3350	3400	3450	3500	3550	3600	3650	3700	3750	3800	3850	3900	3950
τ	0.133	0.119	0.106	0.094	0.085	0.077	0.071	0.065	0.059	0.052	0.046	0.043	0.044	0.046	0.047	0.045	0.047	0.060	0.074	0.080
λ nm	4000	4050	4100	4150	4200	4250	4300	4350	4400	4450	4500	4550	4600	4650	4700	4750	4800	4850	4900	4950
τ	0.073	0.063	0.058	0.057	0.057	0.052	0.045	0.036	0.026	0.016	0.008	0.003	0.001	0.001	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05	<1E-05
λ nm	5000																			
τ	<1E-05																			

